


**Boral Construction Materials
Materials Technical Services**

 Unit 4, 3-5 Gibbon Road
 Baulkham Hills NSW 2153 Australia
 PO Box 400, Winston Hills NSW 2153

 T: +61 (02) 9624 9900
 F: +61 (02) 9624 9999

www.boral.com.au

TEST REPORT – CURING COMPOUND

**Req No: 79587
File No: 130/18**
Laboratory Sample No: 207822
Job description: CURING COMPOUND EVALUATION

Test Method: AS 3799 - 1998

CLIENT: CHEMCOLOUR INDUSTRIES AUSTRALIA PTY LTD

Distributor: PARCHEM CONSTRUCTION PRODUCTS

Sample Identification: Concure HR90 Green

Sample Description: Hydrocarbon resin curing compound

Classification: Class B, Type 1

Source of sample: supplied by client: Chemcolour

Date of sampling: submitted by client: 03/08/2018

Date of test: 03-24/08/2018
Method of application: by spraying at standard application rate of 5m²/L

TEST RESULTS:

Standard property, Test (Method)	Specification	Result	
Water retention efficiency AS 3799.3.1.2 (Method AS 3799 Appendix B)	Min. 90 %	90%	
Non - volatile content AS 3799.3.1.8 (Method AS 1580.301.1/ RTA T865)	N / A	38.8%	NATA accreditation does not cover performance of these tests
Density AS 3799.3.1.9 (Method AS 1580.202.1)	N / A	0.865	
Viscosity AS 3799.3.1.5 (Method AS 1580.214.5)	Min. 0.05 Pa's	0.01 Pa's	
Drying Time AS 3799.3.1.4 (Method AS 1160 Appendix C)	Max. 4 hrs	4 hrs	
Infrared absorption spectrum AS 3799.3.2 (Boral Method)	N / A	attached	
Residue 150µm AS 3799.3.1.6 (Method AS/NZS 2341.20)	Max. 0.2%	0.14%	

The sample submitted and identified by the client.

Juliana Manalang, Mat File, File



Approved Signatory

Julius Alvaro

 Date 10/09/18

Serial No.

171879

Accredited for compliance with ISO/IEC 17025

NATA Accredited Laboratory


Number: 547

CLIENT: CHEMCOLOUR INDUSTRIES AUSTRALIA PTY LTD

BORAL MATERIALS TECHNICAL SERVICES LABORATORY

REQUEST No: 79587

FILE N 130118

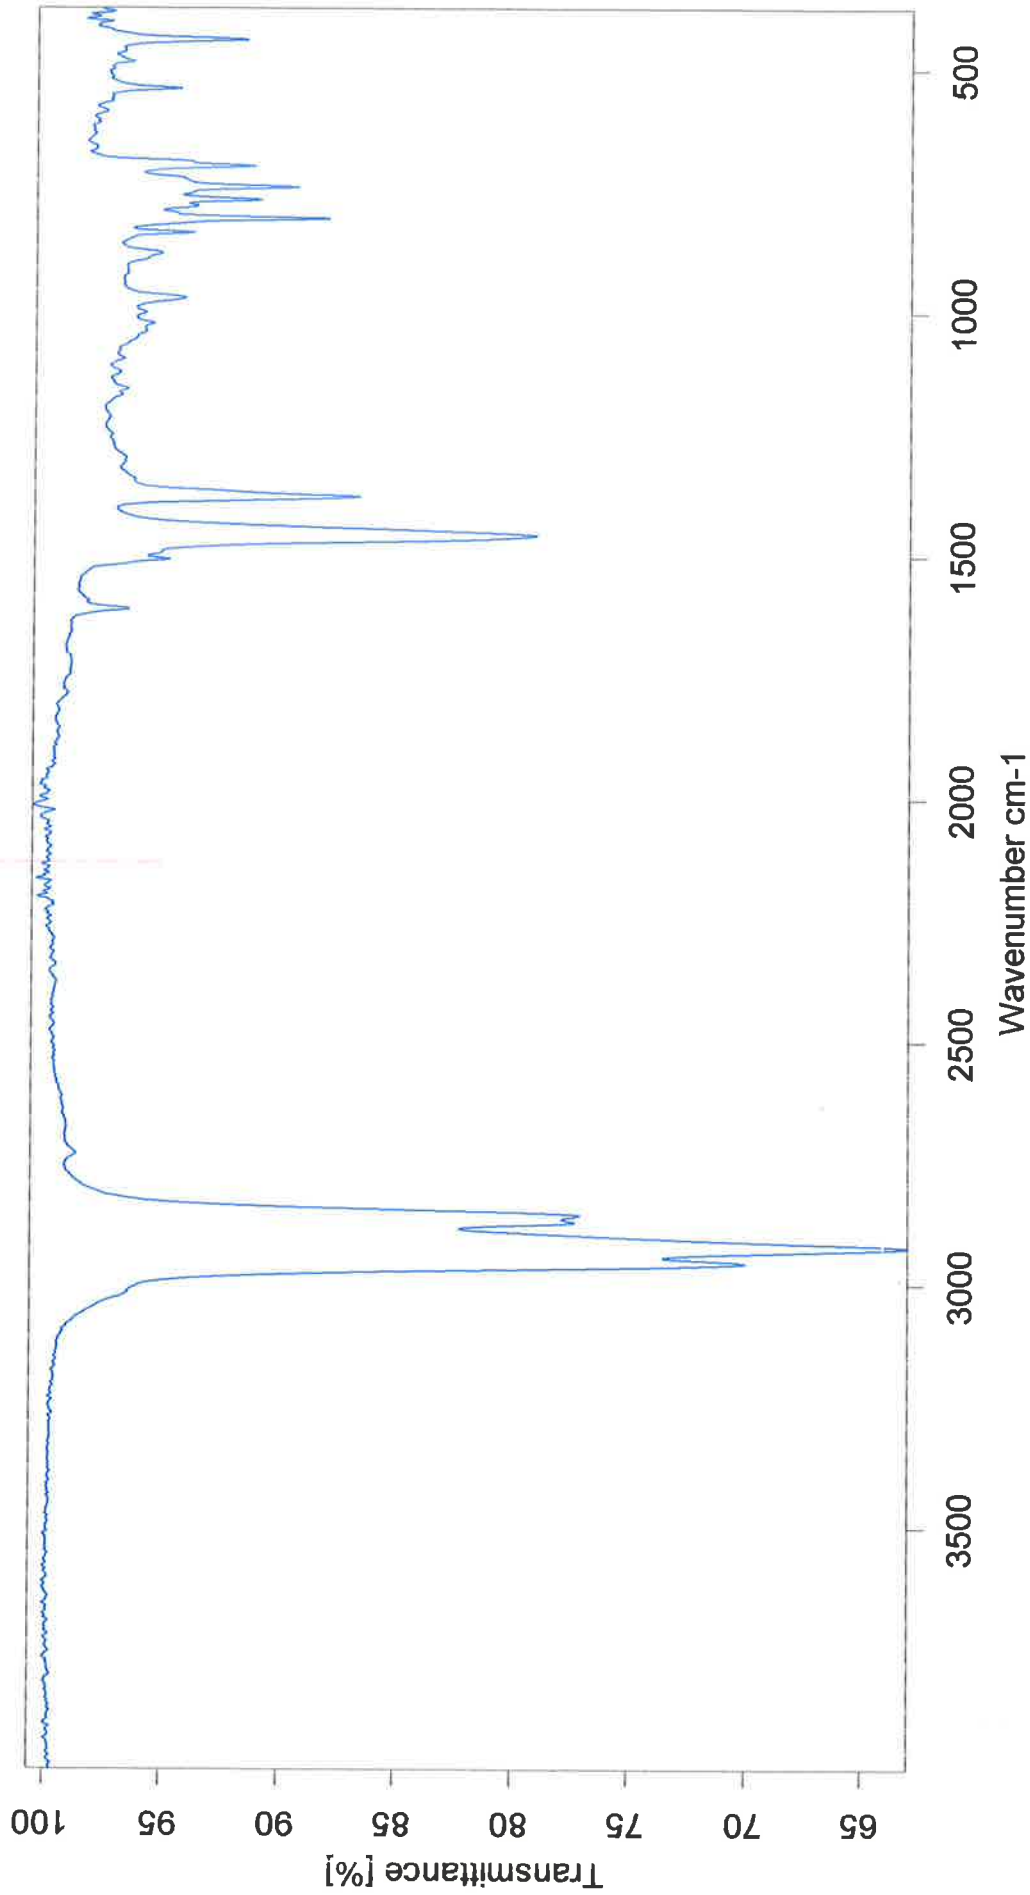

LSN 207822

Concure HR90 Green

Distributor : Parchem Construction Products

NO 10/09/18